

# **Analysis of the skid resistance and adherence between layers of asphalt concretes modified by dry way with polymeric waste**

Lastra-González, P., Indacochea-Vega, I., Calzada-Pérez, M. A., Castro-Fresno, D. & Carpio-García, J.

Author post-print (accepted) deposited by Coventry University's Repository

Original citation & hyperlink:

Lastra-González, P, Indacochea-Vega, I, Calzada-Pérez, MA, Castro-Fresno, D & Carpio-García, J 2017, 'Analysis of the skid resistance and adherence between layers of asphalt concretes modified by dry way with polymeric waste' *Construction and Building Materials*, vol. 133, pp. 163-170.

<https://dx.doi.org/10.1016/j.conbuildmat.2016.12.063>

DOI 10.1016/j.conbuildmat.2016.12.063

ISSN 0950-0618

ESSN 1879-0526

Publisher: Elsevier

**NOTICE: this is the author's version of a work that was accepted for publication in Construction and Building Materials. Changes resulting from the publishing process, such as peer review, editing, corrections, structural formatting, and other quality control mechanisms may not be reflected in this document. Changes may have been made to this work since it was submitted for publication. A definitive version was subsequently published in Construction and Building Materials, 133, (2017) DOI: 10.1016/j.conbuildmat.2016.12.063**

© 2016, Elsevier. Licensed under the Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International  
<http://creativecommons.org/licenses/by-nc-nd/4.0/>

Copyright © and Moral Rights are retained by the author(s) and/ or other copyright owners. A copy can be downloaded for personal non-commercial research or study, without prior permission or charge. This item cannot be reproduced or quoted extensively from without first obtaining permission in writing from the copyright holder(s). The content must not be changed in any way or sold commercially in any format or medium without the formal permission of the copyright holders.

This document is the author's post-print version, incorporating any revisions agreed during the peer-review process. Some differences between the published version and this version

**may remain and you are advised to consult the published version if you wish to cite from it.**

1   **Post-print version:**

2   Lastra-González, P., Indacoechea-Vega, I., Calzada-Pérez, M.A., Castro-Fresno, D., Carpio-  
3   García, J. (2017) Analysis of the skid resistance and adherence between layers of asphalt  
4   concretes modified by dry way with polymeric waste. *Construction and Building Materials*,  
5   133, pp. 163-170. DOI: 10.1016/j.conbuildmat.2016.12.063

7   **Analysis of the skid resistance and adherence between layers of  
8   Asphalt Concretes Modified by Dry Way with Polymeric Waste**

9   Pedro Lastra-González<sup>a,\*</sup>, Irune Indacoechea-Vega<sup>a</sup>, Miguel A. Calzada-  
10 Pérez<sup>b</sup>, Daniel Castro-Fresno<sup>a</sup> and Jaime Carpio-García<sup>a</sup>

11   <sup>a</sup> *GITECO Research Group, Universidad de Cantabria. Avda. de Los Castros s/n.,  
12   39005 Santander, Spain.*

Pedro Lastra-González

[lastragp@unican.es](mailto:lastragp@unican.es)

Irune Indacoechea-Vega

[irune.indacoechea@unican.es](mailto:irune.indacoechea@unican.es)

Daniel Castro-Fresno

[castrod@unican.es](mailto:castrod@unican.es)

Jaime Carpio-García

[jaime.carpio@unican.es](mailto:jaime.carpio@unican.es)

13   <sup>b</sup> *GCS Research Group, Universidad de Cantabria. Avda. de Los Castros s/n., 39005  
14   Santander, Spain.*

Miguel A. Calzada-Pérez

[calzadam@unican.es](mailto:calzadam@unican.es)

15   \* Corresponding author: Pedro Lastra-González

16   E-Mail: [pedro.lastragonzalez@unican.es](mailto:pedro.lastragonzalez@unican.es)

17   Tel.: +34 942 20 39 43

18   Fax: +34 942 20 17 03

19   **Abstract**

20   Skid resistance is one of the most important parameters of a surface mixture due to its  
21   influence on the safety of the road. Besides, the adherence existing between the layers of a  
22   pavement makes these layers work together, which has a great impact in the useful life of the  
23   pavement. The influence on these two parameters of different polymeric waste, which have  
24   been used to modify a mixture by dry way, has been analyzed.

25   The polymeric waste added to an asphalt concrete by dry way are: polyethylene (PE) from  
26   micronized containers, polypropylene (PP) from ground caps, polystyrene (PS) from hangers  
27   and rubber from end-of-life tyres (ELT).

28   The skid resistance and the adherence between layers of the reference and the modified  
29   asphalt concretes have been evaluated separately, so their performance can be compared.

30   The skid resistance has been calculated with the British Pendulum Tester of the TRRL  
31   (Transport Road Research Laboratory) under two conditions: on the mixture just  
32   manufactured and on polished specimens. The adherence between layers was analyzed on

33 asphalt concretes with different texture (AC22 and AC16), applying a direct shear stress at  
34 constant speed in the joint junction (LCB shear test), and undergoing three-layer specimens  
35 to a dynamic shear stress (shear fatigue test designed by the Engineering School of Santander).

36 The results showed that the addition of residual polymers modifies the mixtures surface  
37 properties, and the performance of the asphalt concretes changes greatly depending on the  
38 polymeric waste added.

39 **Keywords:** Skid resistance; Adherence; Asphalt concrete; Polymeric waste; dry way; Modified  
40 mixture.

41 **1. Introduction**

42 Skid resistance and adherence between layers are two basic parameters of a road. While the  
43 first has great influence on the traffic safety (1) , the second is important when it comes to the  
44 pavement useful life (2, 3), due to the fact that adherence between layers makes it possible  
45 that they work together. Thus, this parameter should be properly considered when the  
46 pavement is designed (4).

47 The most important variable that characterizes this property is texture. This is divided into  
48 macrotexture, responsible for drainage and deformation that the wheel suffers when  
49 adapting to the pavement, and microtexture, which breaks the sheet of water and conditions  
50 the punctual contact between wheel and pavement (5, 6).

51 Macrotexture depends on the mixture properties (voids percentage, grain size analysis,  
52 aggregates properties, etc.) while microtexture, on the other hand, depends on the surface  
53 rugosity of the coarse fraction, and is especially influenced by the aggregates polishing, which  
54 wears and becomes rounded at a microscopic scale (7).

55 Adherence between layers is achieved using a tack coat which keeps the joint between them.  
56 Its properties depend on the type of coat employed, the materials used in the bituminous  
57 mixtures, the traffic loads, temperature, and in the case of skid, of macrotexture (3, 8-10). A  
58 good bond between the pavement layers is required to achieve a good performance.  
59 Therefore, the higher the friction between surfaces, the interlocking of the aggregates particle  
60 and the adhesion between the asphalt binder of the two layers and the applied tack coat, the  
61 better will be the adherence between layers (11).

62 For years, different polymers have been used to improve the bituminous mixtures properties.  
63 The rubber began to be used in the sixties to improve skid resistance due to its elasticity and  
64 capacity to break the ice on the road (12). Nowadays, rubber and plastic polymer are used  
65 basically to modify bitumen (13, 14), but their influence on these two properties, adherence  
66 between layers and skid resistance, is not well known.

67 This paper studies the influence that these polymeric waste have on adherence between  
68 layers and skid resistance. For this purpose, an asphalt concrete has been modified by dry way  
69 with 4 different polymers: polyethylene coming from packaging, polypropylene coming from  
70 caps, polystyrene coming from hangers, and rubber coming from end-of-life tyres. Following,  
71 the coefficient of skid resistance has been calculated with the friction pendulum of the TRRL  
72 (Transport Road Research Laboratory), and the adherence between layers has been  
73 determined through the shear stress according to the standard NLT-382/08 and also using  
74 dynamic shear test specifically designed by the Civil Engineering School of Santander (15).

75 **2. Methodology and materials**

76 The reference mixture that has been used is an asphalt concrete (AC22) for surface layer, with  
77 4.8% of penetration grade bitumen (50/70) by weight of mix. The same design process was  
78 used with all the modified mixtures: 1% of aggregates was replaced by volume by each type  
79 of polymeric waste only in the filler fraction by dry way. The rubber has a low influence on the  
80 aggregates and it was mainly mixed with the bitumen, while the plastic polymers were  
81 softened by the hot aggregates and partially coated them, having this way both types of  
82 polymers (rubber and plastic polymers) an influence on the mechanical properties of the  
83 mixture (16) while modifying also its skid resistance and adherence between layers.

84 Four modified bituminous concretes have been manufactured, which have been called: AC22  
85 PE, modified with polyethylene; AC22 PP, modified with polypropylene; AC22 PS, modified  
86 with polystyrene; and AC22 ELT, modified with end-of-life tyres. Besides, an asphalt concrete  
87 AC16 was designed with the same polymers added to the mixture AC22, to study the influence  
88 of the surface texture.

89 The particle size distribution of the polymeric waste is shown in Figure 1.

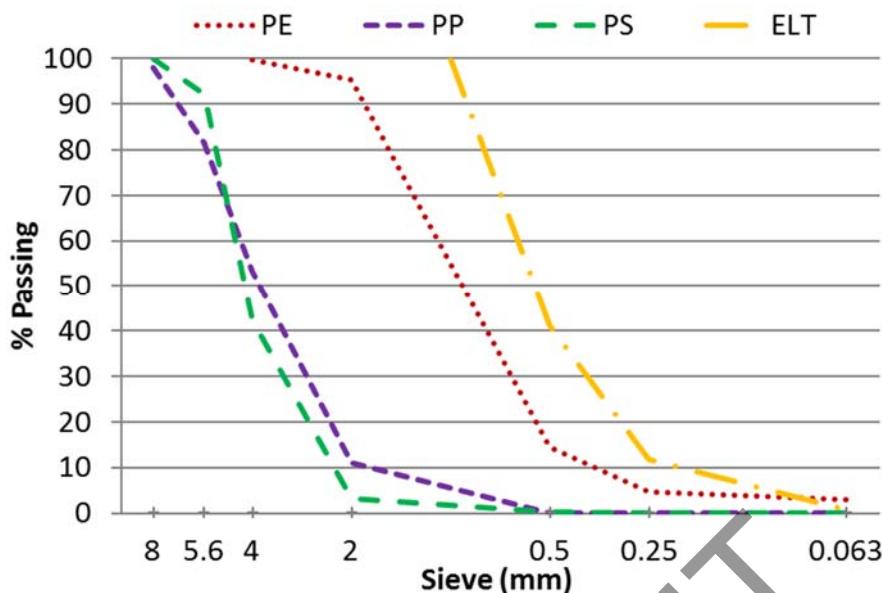


Figure 1. Particle size distribution of waste polymers (16)

## 2.1. Study of skid resistance

Skid resistance was evaluated in two conditions: on new samples without erosion, and on polished specimens; in this way, skid resistance was analysed in the initial and use conditions.

Skid resistance was calculated with the TRRL pendulum on track specimens, as shown in Figure 2.



Figure 2. Evaluation of skid resistance

Four samples of each type of asphalt concrete were employed. The wear procedure was carried out by abrading the wearing course surface. This procedure consisted in sanding 30 times the surface of the specimen in the same direction and sense, with sandpaper grit size 4 (17), trying to keep an even contact pressure, so that in all cases the procedure was performed by the same operator.

104 This procedure was aimed at achieving a similar polished to that of a road in real traffic  
105 conditions. The data obtained by the Public Works Ministry in the highway S-30 in Cantabria  
106 (Spain) were used to assess the abrasion produced on the samples. It was monitored by the  
107 Regional Road Administration between 2009 and 2014. SCRIM (Sideway-force coefficient  
108 Routine Investigation Machine) data were gathered along those years. In order to compare  
109 both measurements (the SCRIM data and the BPN), the correlation obtained by the New  
110 Zealand Transports Agency (18) was used:

$$SC = 0.0071 \cdot BPN + 0.033 \quad (1)$$

111 Where SC is the SCRIM Coefficient of traverse friction and BPN is the value of the British  
112 Pendulum Number, obtained by the TRRL pendulum.

113 This road (S-30) has a traffic category T0 (an average daily intensity of heavy vehicles between  
114 2000 and 4000), an average daily traffic (ADT) of 20000 vehicles, a medium climate area and  
115 a rain area degree 2 (19).

## 116 **2.2. Adherence between layers (shear test and fatigue to shear test)**

117 Adherence between layers was analysed by both shear and fatigue to shear tests. For these  
118 tests, pairs of samples of identical asphalt mixtures (AC22 or AC16) were used. It means that  
119 a sample of the reference mixture was put together with a sample of the same reference  
120 mixture, a PE modified asphalt sample was coupled with other PE modified asphalt sample,  
121 etc. This way, the performance of each polymer can be analysed because the type of polymer  
122 is the only difference between the mixtures.

### 123 **2.2.1. LCB Shear test**

124 At the beginning, the layers adherence was analysed with the LCB shear test (acronym of Road  
125 Research Laboratory of Barcelona in Spanish) (20), which evaluated the adherence of two  
126 specimens by applying a direct shear stress at constant speed in the joint junction  
127 (2.5mm/min), as shown in Figure 3.



128

129

**Figure 3. Test of static adherence between layers**

130 This test is performed at 20°C with at least 7 samples for each mixture type, formed all of  
131 them by two specimens which were joined by 4.1g of conventional emulsion C69B3 ADH (what  
132 is equal to 350g/m<sup>2</sup> of bitumen). The tack coat used was the same in all cases.

133 To find out the influence that the temperature of the mixture surface and the application of  
134 an emulsion has on the adherence, the specimens are compacted at different temperatures  
135 with and without using the emulsion. This analysis is performed only with the mixture  
136 modified with PP (AC22 PP) as representative of the mixtures with polymers, and with the  
137 reference (AC22 REF). The test was done at different conditions:

- 138     i. With emulsion and mixture cold (the common situation): The test was performed  
139         compacting the first layer of the specimen and applying the emulsion when the layer  
140         is cold. Later, the second layer is compacted over the emulsion.
- 141     ii. Without emulsion and mixture cold: the same process was performed, but in this case,  
142         compacting the second layer of the specimen over the first layer without adding the  
143         emulsion; that is to say, after compacting the first layer of the specimen and leaving  
144         it to cold, the second layer was compacted directly on the clean surface of the first  
145         one. By this way, we can analyse the emulsion influence.
- 146     iii. Without emulsion and the mixture hot: in order to evaluate the temperature  
147         influence, the last procedure is repeated. The second layer is compacted over the first  
148         layer without letting the first one to cold and without applying the emulsion between  
149         them.

150 The compaction procedure used for each layer has been in all cases that indicated by the  
151 standard NLT 161/98.

152           **2.2.2. Shear fatigue test**

153 The real performance of the pavement responds to repetitive and short loads (21), so that the  
154 bituminous mixture underwent a dynamic shear fatigue test, applying a parallel load to the  
155 junction levels of the layers. In this way, we can compare the different types of mixtures in  
156 the same conditions, and analyse the adherence between layers under a static and a dynamic  
157 load.

158 The test was carried out at 20°C with 4 three-layer specimens. The specimens were  
159 manufactured with the same emulsion used in the static adherence test (C69B3) and with the  
160 same amount of bitumen (350 g/m<sup>2</sup>).

161 This dynamic test uses a three-layer specimen with measures of 260mm length and 205mm  
162 of width, and 50mm thickness for the central layer and 40mm thickness for the side layers.  
163 The three-layer specimen is supported in the outer layers while the central layer , on which a  
164 vertical sinusoidal load is applied with a frequency of 10Hz and a maximum value of 16KN and

165 a minimum of 3KN (15), remains free of support. This arrangement is shown in Figure 4. The  
166 maximum shear stress reached in each junction surface is 0.22MPa, which is considered as a  
167 representative value of the real conditions (22).

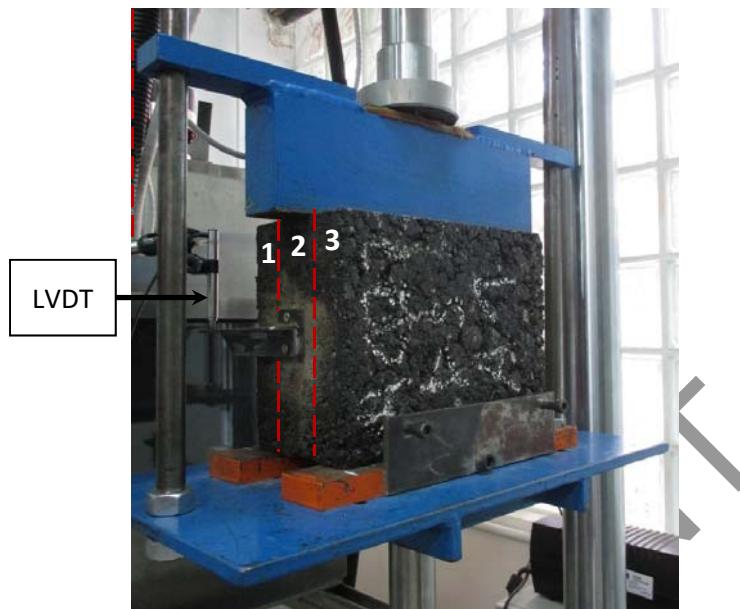


Figure 4. Shear fatigue adherence test

168  
169 As starting hypothesis, it was considered that the energy applied on the central specimen  
170 produced its slip, disregarding any compression or deformation effect on it. To determine the  
171 failure moment, the vertical slip curves of the central specimen are represented in relation to  
172 the number of cycles. These curves are registered with two LVDT comparators placed in the  
173 medium point at both sides of the central specimen.

174  
175 As failure criterion a maximum slip of 10mm was considered, except if any abrupt change in  
176 the slope is produced due to a rearrangement of the specimen, considering, in this case, this  
177 cycle as that of failure.

178 Figure 5 shows the oscillating movement of the central specimen. From this movement, and  
179 considering the amplitude associated to each cycle, and only with the aim to compare the  
180 materials, a parameter  $\alpha$  was estimated that is related with the energy necessary to make the  
181 specimen slip. With this aim, a value of medium strength of 9.5KN ( $F_m$ ) was considered.

182 Data were not taken for every cycle. The test was divided in intervals capturing medium values  
183 that have been considered representative:

$$\alpha = \sum_{i=1}^{N_R} F_m \cdot 2 \cdot A_i \cdot C_i \quad (2)$$

184 Where  $N_R$  is the number of intervals until the failure is produced,  $A_i$  is the medium amplitude  
185 of each interval and  $C_i$  is the number of cycles of the interval.

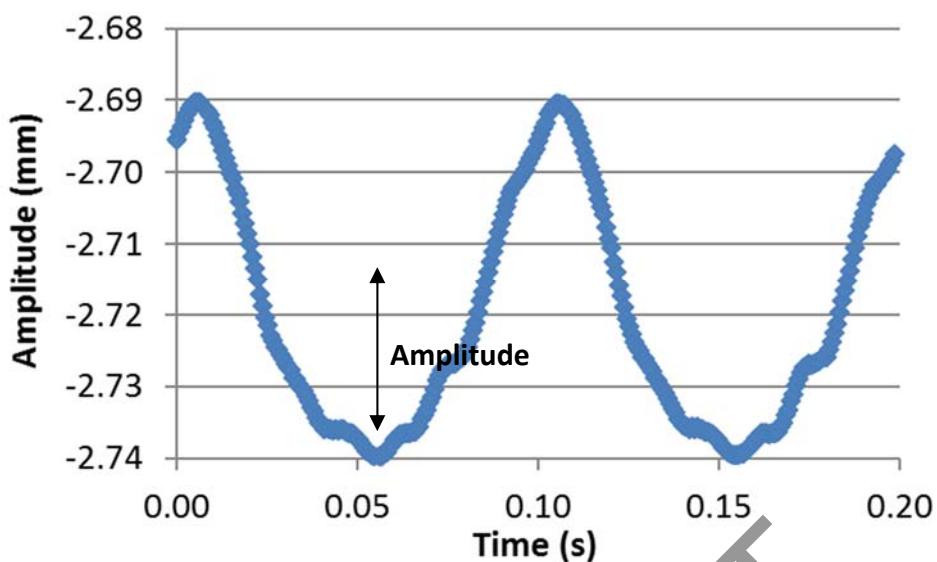


Figure 5. Amplitude of movement of the cycle 160.000 of one AC22 ELT sample

186  
187

188 **3. Statistic analysis**

189 The statistical software IBM SPSS (Statistical Package for the Social Sciences) was used to  
190 determine if the results were significant. The confidence interval considered was 95% (p-value  
191 of 0.05). When the results fulfilled a normal distribution and there was homogeneity of  
192 variances the Scheffe test was used. However, if the results did not comply with the normal  
193 distribution or the homogeneity then, the U of Mann-Whitney test was selected.

194 **4. Results and discussion**

195 **4.1. Evaluation of skid resistance by friction test**

196 Figure 6 shows the values obtained by the British Pendulum Tester (BPT).

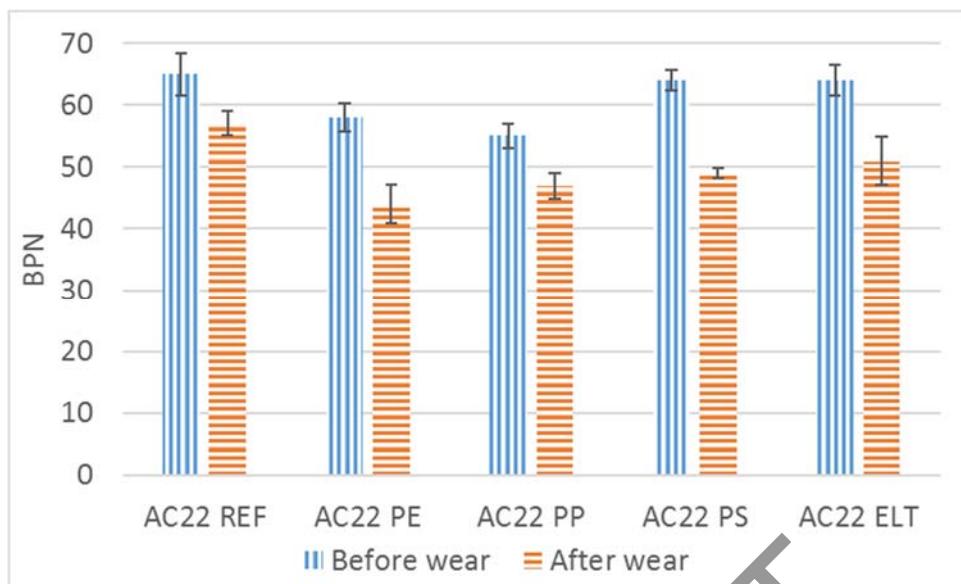


Figure 6. Skid resistance

197

198

199 The results adjust to a normal distribution and there is also homogeneity of variances, both  
200 before and after wearing. Table 1 presents the significances obtained.

201

Table 1. P-value of the skid coefficient for each type of mixture

		PE	PP	PS	ELT
REF	Before wearing	0.041	0.003	0.929	0.978
	After wearing	0.000	0.004	0.024	0.121


202 The skid resistance of the mixtures modified with the additives PS and ELT did not have  
203 meaningful differences with respect to the reference mixture before wear (the p-value is  
204 above that the 0.05 level of significance chosen). However, after wearing, only the ELT mixture  
205 stayed without meaningful differences regarding the reference mixture. The PE and PP reduce  
206 the skid resistance right after they are added to the mixture, while the PS does it after the  
207 mixture is polished. Rubber is the only that keeps the asphalt mixture skid resistance even  
208 after being worn down. These differences can be due to the behaviour of the rubber (it is a  
209 higher friction than plastics) (23), and the fact that it does not coat the aggregates as the  
210 plastic polymers do.

211 The polishing carried out on the specimens was compared with the real wear observed in the  
212 S-30 highway. For the reference mixture the wear produced would be equal to 7 years of  
213 traffic under the same conditions than the S-30. Due to the skid resistance reduction that the  
214 polymers addition causes, the same polishing procedure makes a wear equivalent to 1 year  
215 more of traffic in the case of the AC22 ELT mixture, and approximately 2.5 years in the case of  
216 the AC22 PE mixture, being these two mixtures the most extreme cases.

217 These results must be taken with caution. In the first place, because they are out of the range  
218 of years studied in the real road section (6 years), also because of the variability itself of the  
219 TRRL pendulum test, and finally because of the margin of error that could incorporate the  
220 correlation of results between CRT and BPN.

#### 221 **4.2. Evaluation of the adherence among layers by the shear test (LCB)**

222 The results of the static adherence tests are shown on Figure 7.

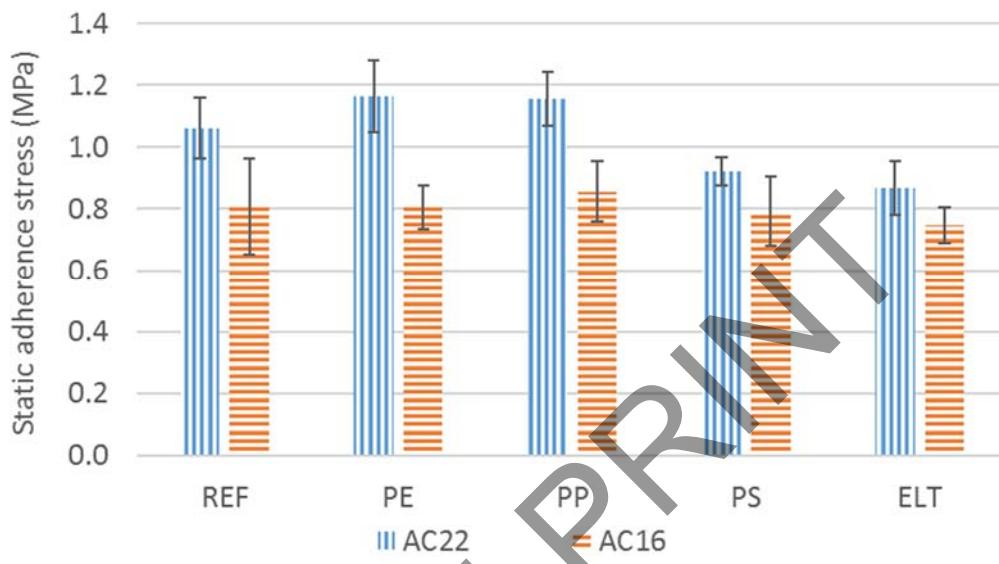

223  
224 **Figure 7. Adherence among layers in front of shear stress**

225 Concerning the AC22 mixture, after verifying the normality and homoscedasticity of the  
226 results, the Scheffe test was performed for each couple of samples. The AC16 mixture did not  
227 show a normal distribution in all cases so that the U of Mann-Whitney test was applied, which  
228 showed that there were not meaningful differences between any of the mixtures. The  
229 significances are shown in Table 2.

230 **Table 2. P-value of the static adherence test with a confidence interval of 95%.**

		PE	PP	PS	ELT
AC22	REF	0.306	0.387	0.087	0.004
AC16	REF	0.325	0.385	0.355	0.064


231 According to the result, the static adherence of the AC16 reference mixtures is not modified  
232 meaningfully by any of the waste polymers. However, in the case of the AC22 mixture, the  
233 addition of rubber from ELT slightly reduces the shear resistance, obtaining a value around  
234 80% of that of the reference.

235 The results were also analysed comparing the data in relation to the maximum aggregate size  
 236 (AC16 vs. AC22). The results showed that the static adherence is significantly greater in the  
 237 case of the AC22 mixes, confirming that the texture has influence on the adherence among  
 238 the layers for all the mixtures. Table 3 summarises the significances.

239 **Table 3. P-value for concretes of the same and different maximum size.**

REF	AC16	PE	AC16	PP	AC16	PS	AC16	ELT	AC16
AC22	0.008	AC22	0.001	AC22	0.001	AC22	0.005	AC22	0.021

240 The influence of the temperature and the coat applied on the adherence between layers is  
 241 shown in Figure 8.

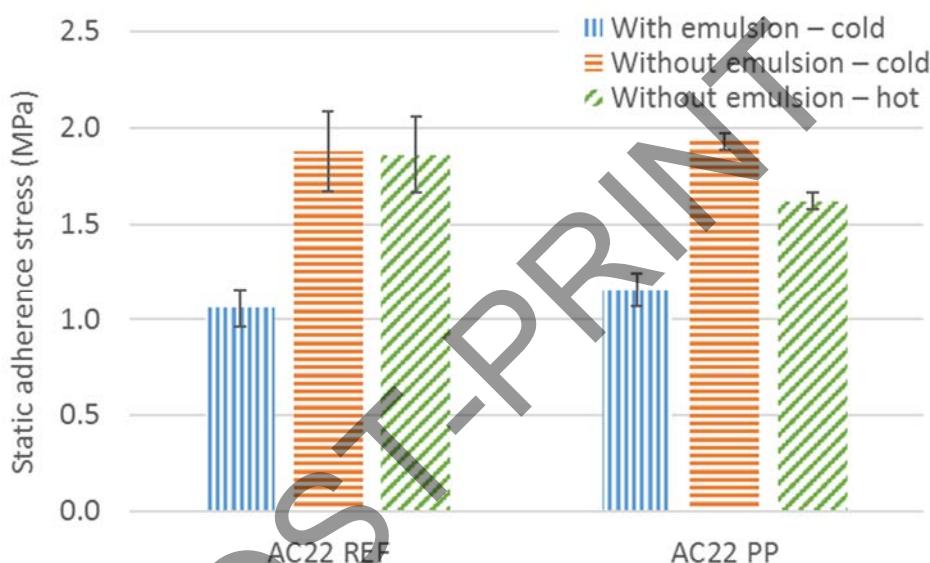

242  
 243 **Figure 8. Shear resistance of the mixture AC22 REF and AC22 PP with and without emulsion**

244 There has not been significant difference between the mixture with PP and the reference  
 245 mixture, being the results coherent with the test previously applied (Figure 7), in which the  
 246 addition of PP did not modify the static adherence. The p-values among mixtures types are  
 247 shown in Table 4 below:

248 **Table 4. P-values of the reference mixture and the modified with PP**

With emulsion – cold	AC22 PP	Without emulsion – cold	AC22 PP	Without emulsion – hot	AC22 PP
AC22 REF	0.387	AC22 REF	0.722	AC22 REF	0.245

249 According to the results shown in Table 5, there have not been significant changes by  
 250 compacting at different temperatures (p-values are above 0.05 both for the reference mixture  
 251 and the PP). However, a higher shear resistance was observed when no emulsion was used.  
 252 Therefore, it may be concluded that to improve the adhere between asphalt layers, the


253 compaction of the second layer over the first layer ensuring a clean surface without emulsion  
254 is more determining than the temperature the lower layer may have.

255 **Table 5. P-values in relation to the compaction temperature and the use of emulsion**

Factor	Conditions	AC22 REF	AC22 PP
Temperature	Cold / Hot	1.000	0.081
Coat	With emulsion / without emulsion	0.019	0.019

256 **4.3. Evaluation of the adherence among layers by the shear fatigue test**

257 The cycles until failure of the shear fatigue test are presented for each mixture type in Figure  
258 9.

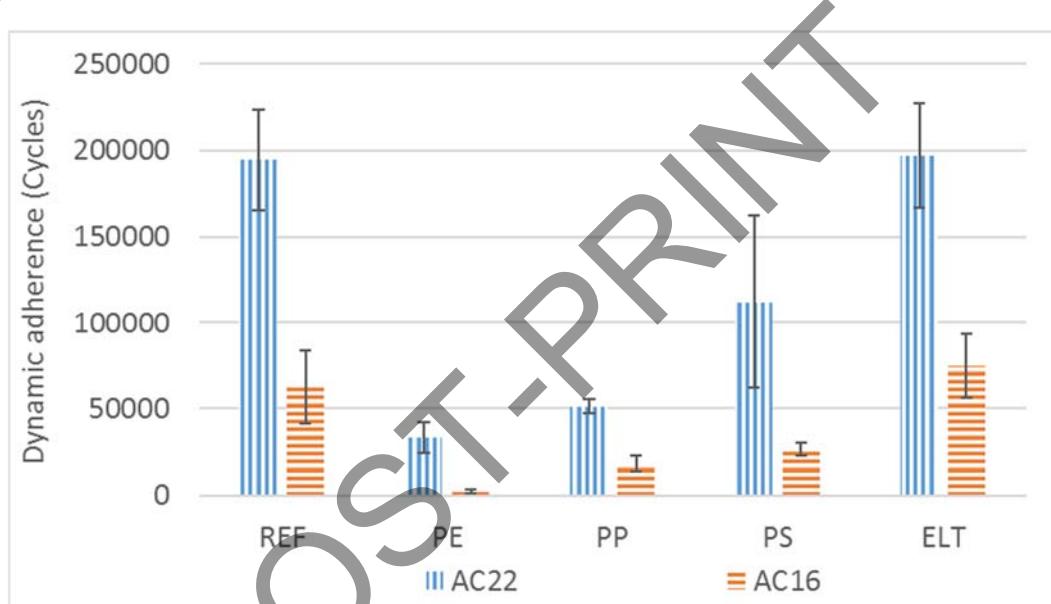

259 **Figure 9. Cycles until failure**

260  
261 The texture of the mixtures becomes again a fundamental parameter, resisting the mixture  
262 AC16 a number of cycles clearly below than AC22 mixture, although the performance of the  
263 mixtures is analogous concerning the type of polymer used.

264 In this case, the results did not adjust to a normal distribution. With regard to the AC22  
265 mixture, the U of Mann-Whitney test showed that there are not significant differences  
266 between the reference mixtures and those modified with PS and ELT, while the adherence  
267 reduces significantly in the case of mixtures with PE and PP. On the other hand, in the case of  
268 AC16 mixtures, only the mixture modified with ELT has a similar performance than the  
269 reference mixture, having the mixtures with PE, PP and PS a significantly lower resistance.  
270 These differences in the performance of ELT regarding the other polymers might be due to its  
271 rubbery state.

272 The significances for both mixtures are presented next on Table 6.

273

Table 6. Significances of the analysis of results of the shear fatigue adherence test.

		PE	PP	PS	ELT
AC22	REF	0.034	0.050	0.077	0.827
AC16	REF	0.021	0.021	0.034	0.386

274 The results of this test, unlike those of the static adherence, show a significant reduction of  
275 adherence when the polymers are added, especially in the asphalt mixes of lower texture  
276 (AC16). Only rubber has the same performance independently of the maximum aggregate  
277 size.

278 As in the static adherence case, it was verified that increasing the aggregate size in turn  
279 increases the shear resistance. Table 7 collects the significances in relation to size.


280 Table 7. Significances of the shear fatigue adherence test in relation to the maximum aggregate size.

REF	AC16	PE	AC16	PP	AC16	PS	AC16	ELT	AC16
AC22	0.034	AC22	0.021	AC22	0.034	AC22	0.034	AC22	0.034

281 The vertical slip of the central specimen until failure was also analyzed, studying its oscillating  
282 movement and the net slip that is produced in each cycle due to the fact that the movement  
283 amplitude is not fully recovered.

284 The net vertical slip is shown in Figure 10. In this figure, it is appreciated that the mixtures  
285 modified with PE and PP have a more fragile performance than the rest. The rubber modified  
286 mixture is the only one with a similar performance to that of the reference, even in the case  
287 of AC16 it increases its resistance (where the texture has a lower influence due to the smaller  
288 maximum aggregate size).


289

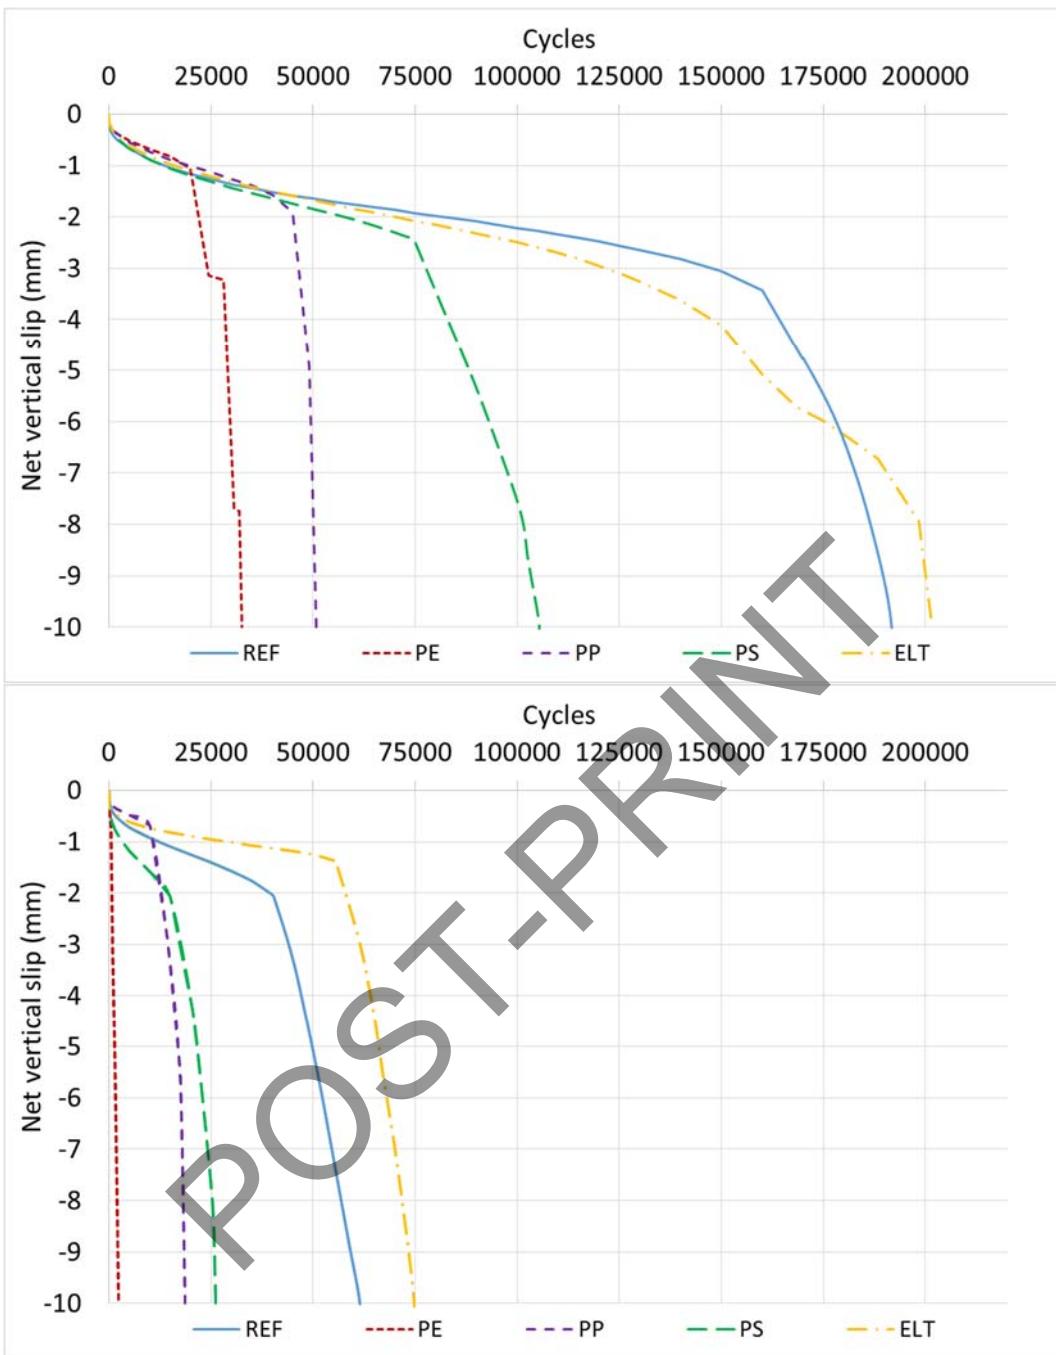

290  
291

Figure 10. From top to bottom: vertical slip curves - cycles for the mixture AC22 and AC16 respectively

292 In Figure 11, the energy parameter  $\alpha$  (estimated with the equation 2) is represented  
293 depending on the number of cycles.

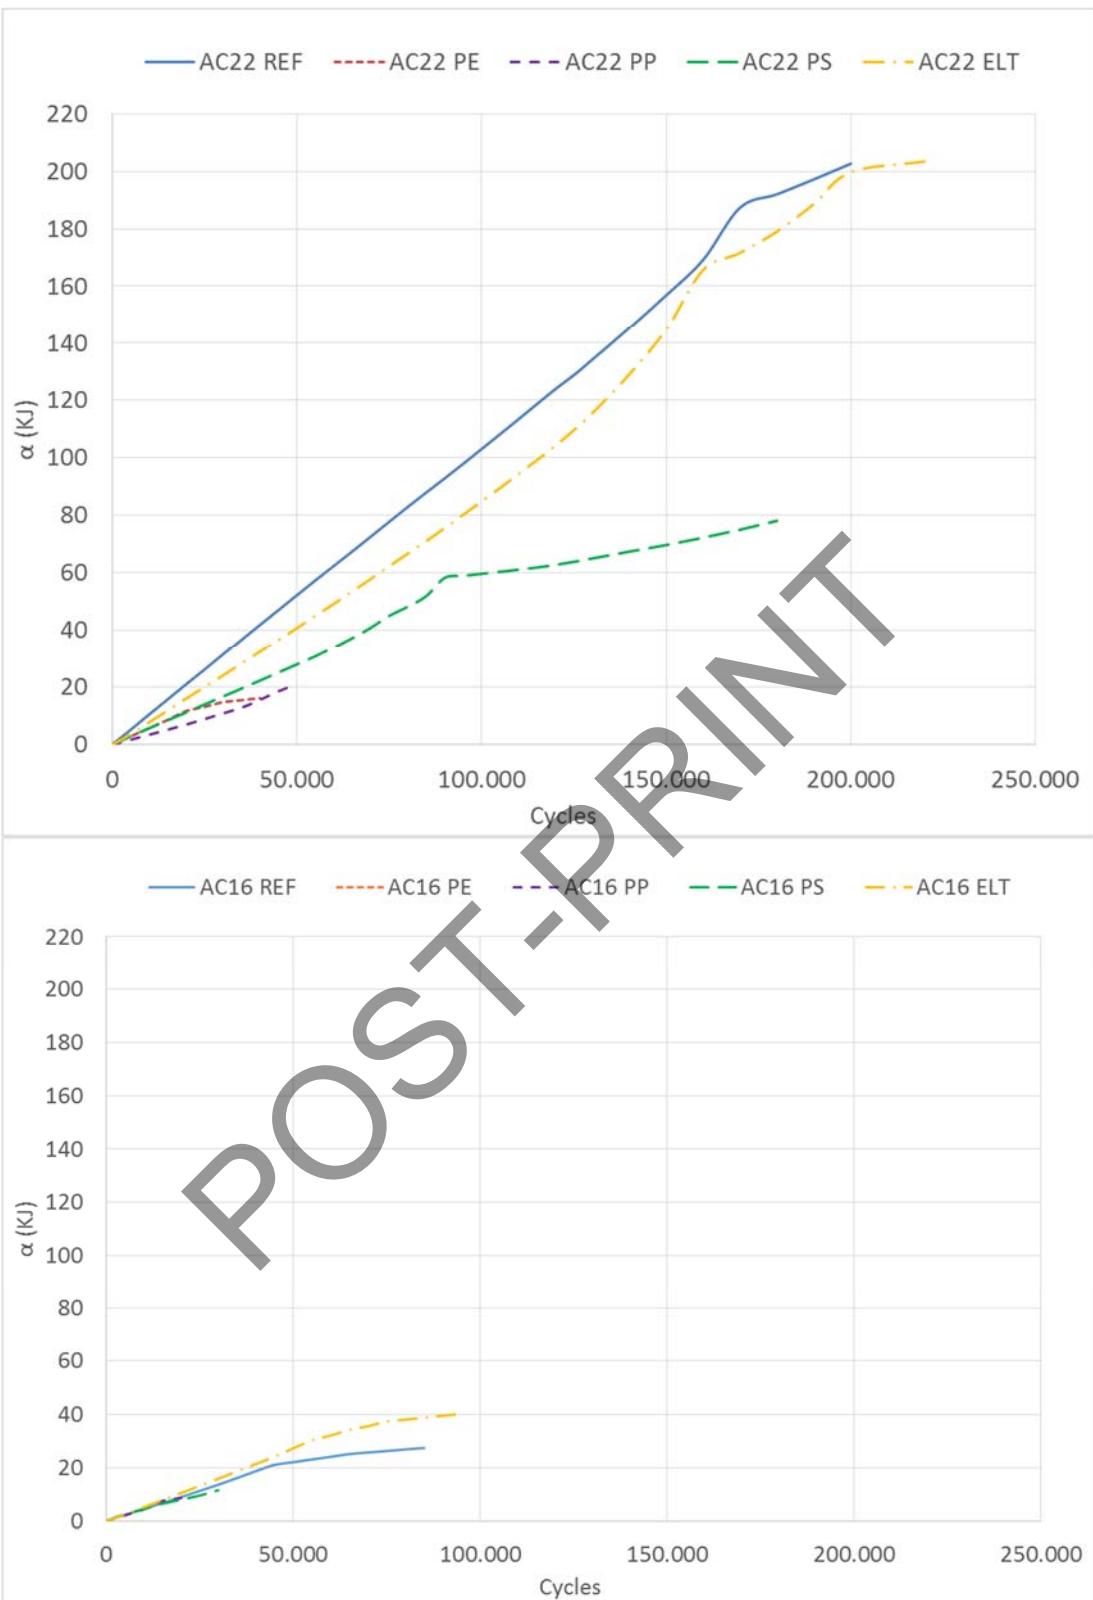

**Figure 11. Parameter  $\alpha$  for each mixture type. A) Top: AC22. B) Down: AC16.**

The curves show a first lineal phase in which energy is proportional to the number of cycles. After this first phase the central specimen may slip suddenly, as in the case of the crystalline polymers (PE and PP), or rather the resistance starts to reduce in front of shear tending the

300 curve to reduce its slope until the failure is produced. The mixtures that in this first lineal  
301 phase have a higher slope, are which achieve greater  $\alpha$  values, and therefore, those which  
302 require higher energy until slip of the central specimen. This is coherent with the fact that a  
303 higher slope implies a more flexible performance.

304 In relation to the polymer used the parameter  $\alpha$  shows great differences. The mixtures with  
305 the crystalline polymers (PE and PP) show values much smaller than the rest, with a more  
306 fragile performance. Rubber is the polymer that reaches the highest values, while PS is in an  
307 intermediate position.

308 These differences may be due to the fact that the emulsion is applied cold, so that the polymer  
309 is in a fully solid state and does not interact with the emulsion residual bitumen. The very  
310 composition of the polymers may be another determining factor. Rubber is the polymer that  
311 has the best performance, what is coherent if we have in mind that it is the only amorphous  
312 polymer that is above its glass transition temperature; that is to say, in rubbery state. In this  
313 way, rubber behaves in a more elastic way increasing the movement amplitude and obtaining  
314 a higher parameter  $\alpha$ .

315 As before, the results are analysed in relation to the maximum aggregate size, to find out if  
316 the texture influence on the results of the  $\alpha$  parameter was statistically significant. The results  
317 had a normal distribution but they did not show homogeneity of variances, so that the U of  
318 Mann-Whitney test was applied by couples in relation to the mixture type. The significances  
319 are shown on Table 8. The results indicate that the texture is a significant parameter for all  
320 the mixtures.

321 **Table 8. Significances of the parameter  $\alpha$  in relation to the aggregate maximum size.**

REF	AC16	PE	AC16	PP	AC16	PS	AC16	ELT	AC16
AC22	0.000	AC22	0.001	AC22	0.012	AC22	0.000	AC22	0.001

322 Considering that the polymers modify the mixture surface properties, the possible relation  
323 between the shear fatigue resistance with the skid resistance of the specimens was analysed.  
324 With this aim, the results of the AC22 mixtures without sanding were used, obtaining a  
325 significant correlation among the shear fatigue resistance and the skid resistance with a  
326 significance of 0.047. This p-value, although near the limit that the confidence interval has  
327 (0.05), shows that the specimens with a higher resistance to skid also present a higher  
328 adherence in the shear fatigue test. This relation is summarized in the following equation,  
329 which obtained a coefficient of correlation of  $R^2=0.74$ .

$$\text{Cycles}_{\text{failure}} = 14982 \text{ BPN} - 799233 \quad (3)$$

330 **5. Conclusions**

---

331 The addition of residual polymers modifies the mixture's surface properties. The plastic  
332 polymers are found in the asphalt layer below their melting temperature (polyethylene and  
333 polypropylene) or glass transition temperature (polystyrene), so that they work in solid state  
334 once the mixture gets cold. However, the rubber works in the asphalt mixture above its glass  
335 transition temperature, therefore in a rubbery state, so that it is more flexible.

336 The polymers reduce the mixture skid resistance, except in the case of rubber. This impact is  
337 especially significant as the mixture is being polished, what is coherent with the statement  
338 that the plastic polymers modify the surface microtexture. The incorporation, therefore, of  
339 plastic polymers to a bituminous mixture in the wearing course demands the implementation  
340 of control measurements that guarantee some minimal values of skid resistance, as it may be  
341 the use of mixtures with higher texture.

342 Respect to adherence among layers, only the AC22 ELT mixture has its static adherence slightly  
343 affected, obtaining a value above 80% of the reference asphalt concrete. The polyethylene,  
344 polypropylene and polystyrene modified mixes withstand greater static loads until their break,  
345 than the rubber. However, in the shear fatigue test, the results differ from those obtained in  
346 the LCB shear test, being the rubber the only polymer which increases the adherence obtained  
347 by the reference mixture, while in the rest of mixtures it is considerably reduced. In both cases,  
348 adherence is also conditioned by the mixture texture, increasing its resistance with the used  
349 aggregate size.

350 The mixtures temperature did not seem to be a significant parameter in the LCB shear test;  
351 however, the resistance to shear increased significantly when the layers were joined without  
352 using a coat, with clean surfaces and under laboratory conditions.

353 With respect to the energy parameter  $\alpha$  necessary to make slip the central specimen, the  
354 mixture with rubber is the only that exceeded the energy of the reference mixture, and  
355 depending on the texture, the energy necessary may be from 4 to 10 times higher than the  
356 requested by the mixtures with polypropylene or polyethylene.

357 **Acknowledgements**

358 POLYMIK is a project financed by the "LIFE+" program of the European Union, with reference  
359 number LIFE10 ENV ES 516. This project was carried out by a consortium coordinated by  
360 GITECO (Construction Technology Applied Research Group, University of Cantabria) and  
361 integrated by ACCIONA Infrastructures, AIMPLAS (Research Association of Plastic Materials),  
362 and VIA-M (Department of Road Construction from the Madrid Regional Government).

363 The authors wish to acknowledge and especially thank Felipe Collazos and the Department of  
364 Public Works and Transport of Cantabria, Belén Monje and Eva Verdejo (AIMPLAS), Raquel  
365 Casado and Elena Sáez (ACCIONA Infrastructures), and Jesús R. Prieto (Universidad de  
366 Cantabria) for their disinterested collaboration.

367

References

- 368 1. Central office, Virginia department of transportation. 2007 Wet accident reduction  
369 program (WARP) report. Virginia, USA.: Virginia department of transportation; 2009.
- 370 2. Kruntcheva MR, Collop AC, Thom NH. Effect of bond condition on flexible pavement  
371 performance. *J Transp Eng.* 2005;131(11):880-8.
- 372 3. Song W, Shu X, Huang B, Woods M. Factors affecting shear strength between open-graded  
373 friction course and underlying layer. *Constr Build Mater.* 2015;101:527-35.
- 374 4. Tschegg EK, Kroyer G, Tan D, Stanzl-Tschegg SE, Litzka J. Investigation of bonding between  
375 asphalt layers on road construction. *J Transp Eng.* 1995;121(4):309-16.
- 376 5. Do M-, Tang Z, Kane M, de Larrard F. Pavement polishing-Development of a dedicated  
377 laboratory test and its correlation with road results. *Wear.* 2007;263(1-6 SPEC. ISS.):36-42.
- 378 6. Oliver JWH. Factors affecting the correlation of skid-testing machines and a proposed  
379 correlation framework. *Road Transp Res.* 2009;18(2):39-48.
- 380 7. Asi IM. Evaluating skid resistance of different asphalt concrete mixes. *Build Environ.*  
381 2007;42(1):325-9.
- 382 8. Kruntcheva MR, Collop AC, Thom NH. Properties of asphalt concrete layer interfaces. *J*  
383 *Mater Civ Eng.* 2006;18(3):467-71.
- 384 9. Raposeiras AC, Vega-Zamanillo Á, Calzada-Pérez MÁ, Castro-Fresno D. Influence of surface  
385 macro-texture and binder dosage on the adhesion between bituminous pavement layers.  
386 *Constr Build Mater.* 2012 3;28(1):187-92.
- 387 10. Yaacob H, Hainin MR, Aziz MMA, Warid MNM, Chang F-, Ismail CR, et al. Bitumen  
388 emulsion in malaysia-a conspectus. *J Teknol.* 2013;65(3):97-104.
- 389 11. Wellner F, Hristov B. Numerically supported experimental determination of the behavior  
390 of the interlayer bond in asphalt pavement. National Research Council; 2015 [cited 19  
391 September 2016].
- 392 12. Hassan NA, Airey GD, Jaya RP, Mashros N, Aziz MA. A review of crumb rubber  
393 modification in dry mixed rubberised asphalt mixtures. *J Teknol.* 2014;70(4):127-34.

- 394 13. Kalantar ZN, Karim MR, Mahrez A. A review of using waste and virgin polymer in  
395 pavement. Constr Build Mater. 2012;33:55-62.
- 396 14. Lo Presti D. Recycled Tyre Rubber Modified Bitumens for road asphalt mixtures: A  
397 literature review. Constr Build Mater. 2013;49:863-81.
- 398 15. Zamora Barraza D. Desarrollo de un procedimiento para la optimización del  
399 comportamiento de un firme flexible mediante el empleo de un geosintético como elemento  
400 antirremonte de fisuras.[dissertation]. Santander, Spain.: Universidad de Cantabria; 2008.
- 401 16. Lastra-González P, Calzada-Pérez MA, Castro-Fresno D, Vega-Zamanillo Á, Indacochea-  
402 Vega I. Comparative analysis of the performance of asphalt concretes modified by dry way  
403 with polymeric waste. Constr Build Mater. 2016;112:1133-40.
- 404 17. Pascual-Muñoz P, Castro-Fresno D, Carpio J, Zamora-Barraza D. Influence of early colour  
405 degradation of asphalt pavements on their thermal behaviour. Constr Build Mater.  
406 2014;65:432-9.
- 407 18. NZ Transport Agency. Notes to the specification skid resistance investigation and  
408 treatment selection. ; 2002.
- 409 19. Ministerio de Fomento. Norma 6.1 IC Secciones de Firme de la Instrucción de Carreteras.  
410 2003.
- 411 20. Miró Recasens R, Martínez A, Peé Jiménez F. Assessing heat-adhesive emulsions for tack  
412 coats. Proc Inst Civ Eng Transp. 2005;158(1):45-51.
- 413 21. Tozzo C, D'Andrea A, Cozzani D, Meo A. Fatigue investigation of the interface shear  
414 performance in asphalt pavement. Modern Applied Science. 2014;8(2):1-11.
- 415 22. Xu Y, Sun L. In: Asphalt layers' shear stress analysis method and its simplified model for  
416 rutting study in asphalt pavement. 4th International Conference on Transportation  
417 Engineering, ICTE 2013; 19 October 2013 through 20 October 2013; Chengdu. ; 2013. p.  
418 2803-14.
- 419 23. Persson BNJ. Theory of rubber friction and contact mechanics. J Chem Phys.  
420 2001;115(8):3840-61.
- 421