

1 Effect of Additive Concentration during Copper Deposition using EnFACE Electrolyte

2 E. M. Dela Pena ^{1,3,4}, N. Bains², A. Hussain², A. Cobley² (FIMF), S. Roy (FIMF)^{1,3}

3 ¹Chemical and Process Engineering, Strathclyde University, James Weir Building, Glasgow,
4 G1 IXJ

5 ²Functional Materials Group, Coventry University, Priory Street, Coventry, CV1 5FB

6 ³School of Chemical Engineering and Advanced Materials, Newcastle University, Merz Court,
7 Newcastle NE1 7RU*

8 ⁴Department of Mining, Metallurgical and Materials Engineering, University of the
9 Philippines, Diliman, Quezon City, 1101, Phillipines

10 Abstract

11 Copper deposition from solutions using high concentration of acid, metal ions and
12 polyethylene glycol (PEG), and bis-(3-sulfopropyl) disulfide (SPS) and chloride ions (Cl⁻) is
13 well known. A recent maskless micropatterning technology, which has the potential to
14 replace traditional photolithographic process, called EnFACE, proposed using an acid-free,
15 low metal ion solution which is in direct contrast to those used in standard plating
16 technology. In this work copper has been deposited using standard electroplating solutions
17 and those used in the EnFACE process. In the standard electrolyte 0.63 M CuSO₄ and 2.04 M
18 H₂SO₄ has been used, along with Gleam additives supplied by Dow Chemicals. For the Enface
19 electrolyte, copper deposition has been carried out using without any acid, and with
20 different concentrations of additives between 17% - 200% of those recommended by
21 suppliers. 25 um of metal has been plated on stainless steel coupons as suggested by and
22 ASTM, peeled off and subjected to ductility and resistance measurements. Scanning
23 electron microscopy and electron back scatter diffraction has been carried out to determine
24 the deposit morphology. It was found that copper deposits obtained from acid-free
25 solutions containing low concentration of metal ion and additives produced copper deposits
26 had properties which are comparable to those obtained from standard electrolytes. The
27 optimum additive concentration for the EnFACE electrolyte was 50% of the recommended
28 value.

29 **Keywords:** EnFACE process, copper film, additives, electrodeposition, electroplating.

30

31 **1.0 Introduction**

32 Copper is the standard metal used in wiring printed circuit boards [1] and
33 interconnects in electronic devices [2]. The standard manufacturing process for both these
34 technologies uses electrodeposition. It is well established that the electrodeposition
35 processes employ electrolyte chemistry of high metal and acid concentrations and employ
36 additives, which impart desirable properties to the plated copper [3]. Numerous studies
37 geared on understanding the role of additives in electroplating have concluded that these
38 chemicals are essential to obtaining metal deposits of high quality [4-9].

39 Recently a new mask-less process, called EnFACE, has been proposed to deposit
40 microscale copper features [10]. As opposed to the standard electrolytes used for PCB and
41 electronic manufacturing, EnFACE proposed a solution using 0.1 M CuSO_4 and no acid [10-
42 15]. Since most of the current literature is has been focused on in understanding the role of
43 additives in the established processes [16-19], the effect on this new chemistry on
44 deposited copper is still unknown. In addition, it is unclear how much additive is required to
45 change deposit properties and what effect they would have on the deposit.

46 This work examines the effect of additives on deposit properties when copper is
47 deposited from EnFACE electrolyte and when additives are added to the bath. The additives
48 used were Gleam A and B (Dow Chemical) which are used in printed circuit board
49 manufacturing. The EnFACE electrolyte consisted of a 0.1 M CuSO_4 solution without addition
50 of acid. Additive levels of 17%, 33%, 50%, 100% and 200% of that recommended by the
51 supplier were added to the solution. In addition, a solution of 0.63 M CuSO_4 with 2.04 M
52 H_2SO_4 with additives as per supplier recommendations was also used in plating experiments.

53 Copper films of 25 μm have been plated on polished steel coupons tests in a beaker
54 without agitation. Deposits were plated from different electrolytes and subjected to
55 ductility and resistivity tests. Deposit morphology was examined by scanning electron
56 microscopy and electron back scatter diffraction. Yield strength and sheet resistance were
57 measured to compare deposit properties against those recommended by Institute of

58 Interconnecting and Packaging Electronic Circuits. Deposit properties are interpreted in
59 terms of additive concentration in the bath. The effectiveness of using low concentrations of
60 metal ions and additives on the influence deposit properties has been assessed.

61

62 **2.0 Experimental**

63 **2.1 Apparatus**

64 Electrodeposition experiments were carried out using a traditional two-electrode
65 plating set-up. The working electrode was a dog-bone shaped stainless steel coupon with an
66 area of 31.92 cm². The counter electrode was a copper rod with an exposed area of 58.1
67 cm². Plating was done in a 2-litre cell using the appropriate plating solution, and the current
68 source was a Thurlby Thundar PL-310 power unit.

69

70 Morphological analysis (SEM and EBSD) was done using the JEOL JSM-5300LV.
71 Resistivity of the plated films were measured using the Signatone Pro4 (four point probe)
72 system in the Electronics and Electrical Engineering department Newcastle University UK.
73 Mechanical properties were characterized using a Tinius Olsen H50KS with Horizon software
74 for data recording. All tensile tests followed the ASTM E-345 [20], a standard for
75 determining tensile properties of metallic films. Morphological and mechanical
76 characterization were conducted in the Advanced Chemical and Materials Analysis (ACMA)
77 laboratory, Newcastle University.

78

79 **2.2 Chemicals and Electrolytes**

80

81 Steel coupons (308 stainless) were manufactured to the specifications of IPC-TM-650
82 (IPC-TM stands for The Institute for Interconnecting and Packaging Electronic Circuits
83 Testing Methods) standard. Technical grade CuSO₄ and H₂SO₄ (Sigma-Aldrich) were used to
84 prepare the plating electrolyte. The additives used were commercially available Copper
85 Gleam series (Rohm Haas). Copper Gleam HS – 200 A served as the accelerator (SPS), while
86 Copper Gleam B was the inhibitor (PEG). The Cl⁻ ions were sourced from concentrated HCl
87 (37%, Sigma Aldrich). Chemicals for pre-treatment of the coupons include concentrated

88 HNO₃ and ethanol (Sigma Aldrich). The PRP200 photoresist (Electrolube) was used to
89 insulate the backside of the coupons. Table 1 lists the composition of the different plating
90 baths used for copper deposition.

91

92 **2.3 Procedure**

93 Prior to actual plating, the stainless steel coupons were cleaned with concentrated
94 HNO₃, and then rinsed with water for 1 minute. The coupons were mechanically polished
95 using silicon carbide sheets, starting at grit #220 and progressing to grit #4000. One side of
96 the coupon was coated with the photoresist, and left to dry. The exposed side of the coupon
97 was swabbed with ethanol for 30 seconds and again allowed to dry.

98 Electrodeposition was carried out in direct current (DC) mode. The counter and
99 working electrode was set-up in the plating cell containing different electrolytes. Table 2
100 shows the plating parameters used for the different experiments. These parameters were
101 derived from polarization experiments that yielded limiting current regarding each bath
102 type. Since the deposits become rougher as they approach the limiting current [21], the
103 current was set at a fraction of this value to ensure that dendritic copper was not plated.
104 The total plating time was calculated to obtain a copper film with thickness of 25 μm .

105 After the allotted deposition time was reached, the coupons were removed from the
106 solution and washed with deionized water for 1 minute. The surface was dried using a lint
107 free cloth and left to dry in air. The plated copper films were then carefully peeled off from
108 the stainless steel substrate, and were prepared for subsequent characterization. Each
109 experiment was repeated three times to check for reproducibility.

110 For SEM and EBSD analysis, a 2x2 cm² area was cut out from the central portion of
111 the copper coupon. For mechanical and resistivity testing, the whole coupon was used.
112 Necessary care was taken to prevent damage on the coupons, particularly during handling
113 and specimen mounting in the UTM that would compromise the quality of results of the
114 mechanical tests. The values reported in this manuscript are the average of measurements
115 from three different films.

116

117 3.0 Results and Discussion

118 3.1 Morphology and Grain Size Measurements

119 Figure 1 shows the SEM images (planar view) of the products of the EnFACE bath
120 with different additive concentration and the standard bath. It can be observed that as the
121 amount of additive increased, the surface roughness of the deposit from the EnFACE bath
122 noticeably decreased. In fact, the product of the bath with 100% and 200% additive
123 concentrations appeared the smoothest and most compact among the lot. On the other
124 hand, in terms of appearance, the deposit from the standard copper bath is similar to that
125 of the E-33 and E-50 EnFACE bath, which showed that even at low concentrations the
126 influence of additives is substantial.

127 The observed reduction in surface roughness may indicate the occurrence of a fine-
128 grained structure in the deposit. However, attempts to quantify the grain size of the copper
129 films proved difficult since the grain structures were not easily discernible, even when
130 viewed at high magnifications. Therefore, it became necessary to use another imaging
131 technique that allowed accurate visualization of grain morphology. Electron back-scatter
132 diffraction (EBSD) was chosen because the technique allows grain size and grain orientation
133 analysis without the need to alter the surface condition of the metal.

134 Figure 2 shows the corresponding EBSD maps for the products of the EnFACE bath
135 with different levels of additive concentration, and of the standard copper bath. The EBSD
136 images revealed the grain structure, which were predominantly equiaxed for the electrolyte
137 without additives, and becomes smaller as additive concentration is increased. The EBSD
138 data allowed measurement of the grain size of deposits.

139 The rightmost column in Table 2 gives a summary of the calculated grain size of
140 deposits measured using the EBSD image analyzing software TANGO (HKL Technology A/S,
141 2001). The grain structure map produced in EBSD was processed by performing noise
142 reduction and wild spikes extrapolation. The band contrast was adjusted to clearly see the
143 grains. The grain size parameter used is the major and minor axis of the fitted ellipse and
144 the software automatically measures the grain size based on the delineation of all of the
145 grain boundaries.

146 Similar to the conclusions made from SEM analysis, the EBSD results indicated that
147 additives created a finer grain structure in the deposit, and that the decrease in grain size
148 was proportional to the concentration of additives used. The appearance of small grains
149 inside the larger ones was further analyzed, and these small grains were identified as sub-
150 grains brought about by recrystallization. Dynamic recrystallization or self-annealing is a
151 recognized phenomenon that exclusively occurs in copper plated from additive-containing
152 electrolytes [22].

153 The SEM and EBSD results validate the grain-refining action of additives on the
154 copper deposits. While numerous studies have reported similar observations in
155 conventional copper baths [23, 24, 25], these observations may be the first report on the
156 effect of additives used for super-filling on the products of the EnFACE bath. It is also
157 observed that the grain refining effect of additives on the EnFACE bath is more pronounced
158 than in the standard bath. This was seen with the finer grain size obtained in the EnFACE
159 copper compared to the standard copper at the same additive concentration.

160 Grain refinement is one of the most important morphological and structural effects
161 of additives [24]. It is known that additives affect the mechanisms of nucleation and growth
162 during plating [26]. For example, brighteners enhance nucleation rates, while leveling
163 agents inhibit dendritic growth. Both these actions can contribute to creating the fine-
164 grained structure seen in the deposits. The effect could even be synergistic when different
165 types of additives are present in the electrolyte. Since, grain refinement would affect the
166 mechanical and electrical properties, these properties were measured and are reported
167 below.

168

169 **3.2 Mechanical and Resistance Measurements**

170 Figure 3 shows the resistivity measurements for different additive concentration
171 using EnFACE electrolyte. Clearly, the progressive addition of additives created a more
172 resistive copper deposit. Furthermore, the resistivity of some of the EnFACE copper is
173 similar in value to copper deposited from a standard electrolyte; i.e., the resistivity is 2.27
174 $\mu\text{ohm-cm}$ when copper is plated from a standard bath, and 2.30 and 2.31 $\mu\text{ohm-cm}$ when
175 deposited from E-33 and E-50, respectively.

176 The increase in the resistivity of the copper film is explained by the significant
177 reduction of grain size brought about by additive use. Morphological analysis presented
178 earlier has already confirmed a change in grain size. Grain boundaries, together with other
179 defects, act as electron scattering centers and reduce the effective displacement of the free
180 electrons during electronic conduction [27]. Thus, the increase in grain boundary area
181 during grain refinement caused the increase resistivity of the deposited film.

182 Figure 4 shows the plot of mechanical properties; namely, 0.2% offset yield strength
183 (YS), ultimate tensile strength (UTS), and the ductility of the electrodeposited copper films,
184 as a function of additive concentration. The results reveal the strong effect of additive
185 concentration on mechanical properties. Both YS and TS increased while ductility decreased
186 with increasing additive concentrations. The percent increase in YS and TS, and the %
187 decrease in ductility are almost similar; a ~40% change in value from the lowest to the
188 highest additive concentration.

189 Table 3 summarises the mechanical properties of copper plated from a standard
190 bath. The Institute for Interconnecting and Packaging Electronic Circuits advises that copper
191 for interconnects to have a minimum tensile strength of 207 MPa and ductility of 3% [28].
192 Using these values, it can be seen that plated films from EnFACE electrolytes are closer to
193 the specification of the Institution than those obtained from the standard electrolyte. It is
194 envisaged that by optimising bath and plating conditions, the specifications for
195 interconnections and packaging can be achieved.

196 The observed trends in the plated copper are consistent with the well-known
197 mechanical behavior of metals. Typically, an increase in the metal's strength will be
198 accompanied by a loss in ductility. The results also indicate a clear improvement in the
199 mechanical strength of the plated copper when additives are used with the bath. To explain
200 how additive concentration affects mechanical properties, one needs to consider the plated
201 metal's inherent microstructural features. Important microstructural features include
202 dislocation, grain boundaries and voids [25].

203 It is reasonable to assume that the observed grain size refinement directly caused
204 the changes in the metal's yield strength and ductility; a statement consistent with
205 published work [29, 30, 31]. Classical theories on slip and plastic yielding explain how grain

206 boundaries can serve as dislocation barriers, thereby lowering dislocation mobility and
207 preventing easy plastic deformation to occur. Consequently, such an action increases YS and
208 lowers ductility. Tensile strength, on the other hand, is strongly affected by the amount of
209 voids, and an inverse relation exists between the two.

210

211 **3.3 Optimum Additive Concentration**

212 By inspecting the properties of the copper plated from EnFACE electrolytes
213 containing different concentration of additives, it was found that at an additive
214 concentration of 50%, the plated copper has properties close to the specifications stated by
215 IPC. Though the properties of the E-50 electrolyte is slightly different from the values
216 specified, they are closer than those obtained from a standard electrolyte. It can be
217 envisaged that further improvements in deposit properties could be obtained by optimising
218 plating conditions.

219 Notably, the EnFACE electrolyte has a low metal ion concentration, which can limit
220 plating rates (c.f. Table 2). In fact, the plating rate of the standard electrolyte is nearly four
221 times higher than the best EnFACE electrolyte (E-50). This means that the rate of plating
222 needs to be increased by improving agitation. In many industries, such as circuit board
223 manufacturing, plating rates of 1.5-2.0 ASD (15 - 20 mA/cm²) are advised. Since all of the
224 EnFACE electrolytes exceed this plating rate, it should not affect plating rates in an industrial
225 environment. On the other hand, by operating baths which have low metal and additive
226 concentration, savings and sustainability can be achieved.

227

228 **4.0 Conclusions**

229 Copper was successfully plated from the additive containing EnFACE bath, and its
230 properties were characterized and compared to that achieved using a standard electrolyte.
231 Stainless steel coupons were plated with 25 um copper films using electrolytes of different
232 additive concentrations. Additives caused the refinement of the grain structure of deposits,
233 and the decrease in grain size was proportional to the concentration of additive used. This
234 grain refinement consequently increased resistivity, yield and tensile strength, and reduced

235 the ductility of plated copper. The EnFACE bath required a lower amount of additive to
236 obtain a product that has comparable properties to that obtained from a standard
237 electrolyte. The optimum additive concentration appears to be about 50% lower than the
238 industry recommended dosage.

239

240 **Acknowledgement**

241 This work was supported by MESMOPROC (www.mesmoproc.eu) funded by the EACI Grant
242 MP1307.

243 *This work commenced in Newcastle University. Both Newcastle authors have changed
244 their affiliation to Strathclyde University.

245

246

247

248 **References**

- 249 [1] P.C. Andricacos, C. Uzoh, J.C. Dukovic, J. Horkans and H. Deligiani, IBM J. Res. Dev. (1998)
250 42, 567.
- 251 [2] S. Franssila, 2nd Edition, John Wiley & Sons Ltd (2010), West Sussex, United Kingdom.
- 252 [3] A. Brenner, Academic Press (1962), New York.
- 253 [4] S.S. Kruglikov, N.T. Kudriavtsev, G.F. Vorobiova and A.Ya. Antonov, Electrochimica Acta
254 (1965), 10, 253-261.
- 255 [5] G. Fabricus and G. Sundholm, Journal of Applied Electrochemistry (1985) 15, 797 – 801.
- 256 [6] T.C. Franklin, Surface and Coating Technology (1987), 30, 415 – 428.
- 257 [7] L. Oniciu and L. Muresan, Journal of Applied Electrochemistry (1991), 565-574.
- 258 [8] E. Michailova, I. Vitanova, D. Stoychev, and A. Milchev, Electrochimica Acta (1993),
259 38(16), 2455-2458.
- 260 [9] J.J. Kelly, C. Tian and A.C. West, Journal of Electrochemical Society (1998), 146 (7) 2540 –
261 2545.
- 262 [10] S. Nouraei and S. Roy, Electrochimica Acta (2009), 54, 2444-2449.
- 263 [11] Roy, S. 2007. Journal of Physics D: Applied Physics. Vol. 40(22), R413-R426.
- 264 [12] Q. Wu, T.A. Green and S. Roy, Electrochemistry Communications (2011), 13, 1229-1232.
- 265 [13] S. Coleman, and S. Roy, Chemical Engineering Science (2014), 113, 35-44.
- 266 [14] S. Coleman and S. Roy, Journal of Applied Electrochemistry (2015), 45 (8), 889-898.
- 267 [15] I. Schönenberger and S. Roy, Electrochimica Acta (2005), 51, 809-19.
- 268 [16] U. Landau, Plenum Press (1982), New York.
- 269 [17] L.N. Schoenberg, J. Electrochem. Soc. (1971), 118(70), 1571-1576.
- 270 [18] M. Paunovic and R. Arndt, J. Electrochem. Soc. (1983), 130, 794-799.
- 271 [19] T.P. Moffat, D. Wheeler and D. Josell, The Electrochemical Society Interface, Winter
272 2004.
- 273 [20] ASTM E-345 Standard Test Methods of Tension Testing of Metallic Foil.
- 274 [21] T.P. Moffat, D. Wheeler, C. Witt and D. Josell, Electrochem. and Solid-State Lett. (2002),
275 5, C110-C112.

- 276 [22] C. Cabral Jr., C. Andricacos, L. Gignac, IC. Noyan, K.P. Rodbel, T.M. Shaw, R. Rosenberg,
277 and JME Harper, Abstracts of the Advanced Metallization Conference (AMC), October 6-8,
278 1998, Colorado Springs, Colorado.
- 279 [23] M. Paunovic and R. Arndt, Surface Preparation and Finishes for Metals. J. Electrochem.
280 Soc. (1983), 130, 794-799.
- 281 [24] L. Oniciu and L. Muresan, Journal of Applied Electrochemistry (1991), 21, 565-574.
- 282 [25] D. Dini and D. Snyder, Modern Electroplating: 5th Edition” Edited by Mordechay
283 Schlesinger, Milan Paunovic, John Wiley and Sons (2010), NY.
- 284 [26] M. Tan, C. Guymon, D. Wheeler, and J. Harb, J. Electrochem. Soc. (2007) 154(2), D78-
285 D81.
- 286 [27] W. Callister W, Materials Science and Engineering: An Introduction. 7th edition,
287 Hoboken, NJ : John Wiley & Sons (2007).
- 288 [28] IPC-TM-650 test methods manual. Number 2.4.18. The Institute for Interconnecting and
289 Packaging Electronic Circuits, 2215 Sanders Road, Northbrook, IL.
- 290 [29] E.M. Hofer and H.E. Hintermann, Journal of the Electrochemical Society (1965), 112,
291 167-173.
- 292 [30] E. Michailova, I. Vitanova, D. Stoychev and A. Milchev, Electrochimica Acta (1993),
293 38(16), 2455-2458.
- 294 [31] E. Rusli, F. Xue, T. Drews, P. Vereecken, P. Andricacos, H. Deligianni, R. Braatz and R.
295 Alkire, Journal of the Electrochemical Society (2007), 154 (11) D584 – D597.

296
297
298
299
300
301
302
303

304 **Figure Captions**

305 Figure 1: SEM images of copper deposits from EnFACE bath with different additive
306 concentration: a) E-17 with 17% additive concentration, b) E-33 with 33% additive
307 concentration, c) E-50 with 50% additive concentration, d) E-100 with 100% additive
308 concentration and e) E-200 with 200% additive concentration, and f) S - standard bath.
309 These percentages are relative to the industry recommended additive concentration of 10
310 ml/L Copper Gleam B, 0.5 ml/L Copper Gleam A, and 70 ppm Cl⁻.

311

312 Figure 2: EBSD images of copper deposits from EnFACE bath with different additive
313 concentration: a) E-17 with 17% additive concentration, b) E-33 with 33% additive
314 concentration, c) E-50 with 50% additive concentration, d) E-100 with 100% additive
315 concentration and e) E-200 with 200% additive concentration, and f) S - standard bath.
316 These percentages are relative to the industry recommended additive concentration of 10
317 ml/L Copper Gleam B, 0.5 ml/L Copper Gleam A, and 70 ppm Cl⁻. The calibration bar is for 2
318 um length. The different colors in the EBSD map represent different crystals planes as
319 described by the g) inverse pole legend.

320

321 Figure 3: Resistivity measurements of electrodeposited copper films using EnFACE
322 electrolyte with varying additive concentrations.

323

324 Figure 4: The a) yield strength, b) tensile strength and ductility of plated copper films using
325 EnFACE electrolyte with varying additive concentrations.

326

327

328

329

330

331

332

333

334

335 **Table 1: Bath composition and nomenclature.**

Designation	Setting description	Cu ₂ SO ₄ M	H ₂ SO ₄ M	Gleam B ml/L	Gleam A ml/L	HCl ppm
S	Standard bath	0.63	2.04	10	0.5	70
S-0	Standard bath without additives	0.63	2.04	X	X	X
E-0	EnFACE bath without additives	0.1	X	X	X	X
E-17	17% of the recommended additive concentration	0.1	X	1.7	0.08	12
E-33	33% of the recommended additive concentration	0.1	X	3.3	0.17	23
E-50	50% of the recommended additive concentration	0.1	X	5.0	0.25	35
E-100	Recommended additive concentration	0.1	X	10.0	0.50	70
E-200	High concentration (double of the recommended additive)	0.1	X	20.0	1.0	140

336

337 "S" stands for "standard" electrolytes based on supplier recommendation and "E" stands for
338 "Enface" baths. The number following the "S" and "E" stand for the percent of additive
339 concentration added to the electrolyte

340

341

342 **Table 2: Plating parameters**

343

344

345

346

347

348

349

350

351

352

Electrolyte	Plating current mA (40% from I_{LIM})	Plating time minutes	Grain size From EBSD (nm)
S	245	146	431
S-0	255	152	11524
E-0	68	615	9016
E-17	68	623	758
E-33	63	623	523
E-50	58	669	466
E-100	54	705	407
E-200	53	708	400

353

354

355

356

357

358 **Table 3: Mechanical properties of copper plated from S, S-0 and E-50 bath.**

359

Bath	YS _{0.2%} , MPa	TS, MPa	Ductility, %
S	219	256	1.69
S-0	136	145	2.77
E-50	170	213	2.17

360

361

362

363

364

365

366

367


368

369

370

371

372

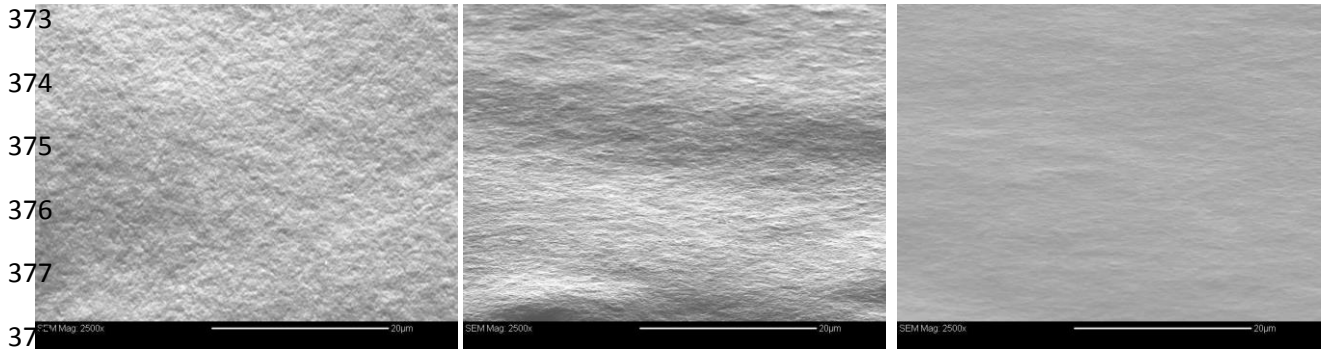

a) E-17

b) E-33

c) E-50



d) E-100

e) E-200

f) S

Figure 1: SEM images of copper deposits from EnFACE bath with different additive concentration: a) E-17 with 17% additive concentration, b) E-33 with 33% additive concentration, c) E-50 with 50% additive concentration, d) E-100 with 100% additive concentration and e) E-200 with 200% additive concentration, and f) S - standard bath. These percentages are relative to the industry recommended additive concentration of 10 ml/L Copper Gleam B, 0.5 ml/L Copper Gleam A, and 70 ppm Cl⁻.

402

403

404


405

406

407

408

409

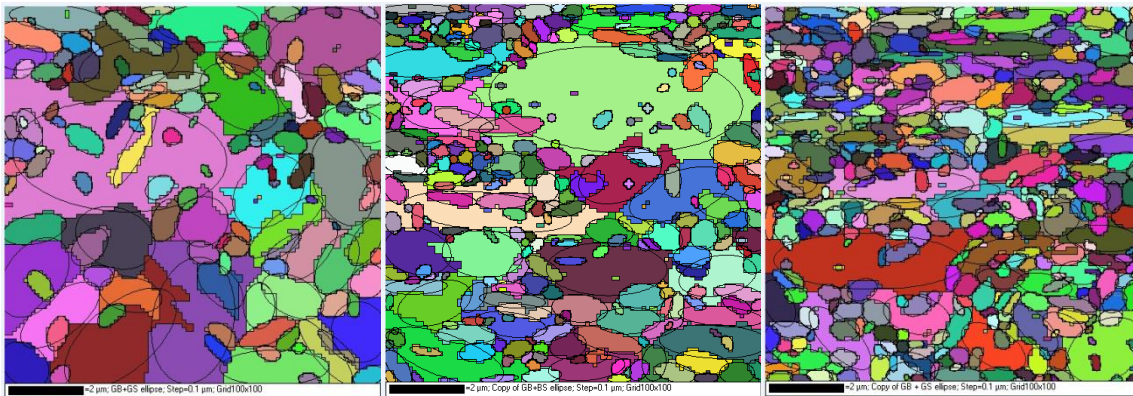

410

a) E-17

b) E-33

c) E-50

411

412


413

414

415

416

417

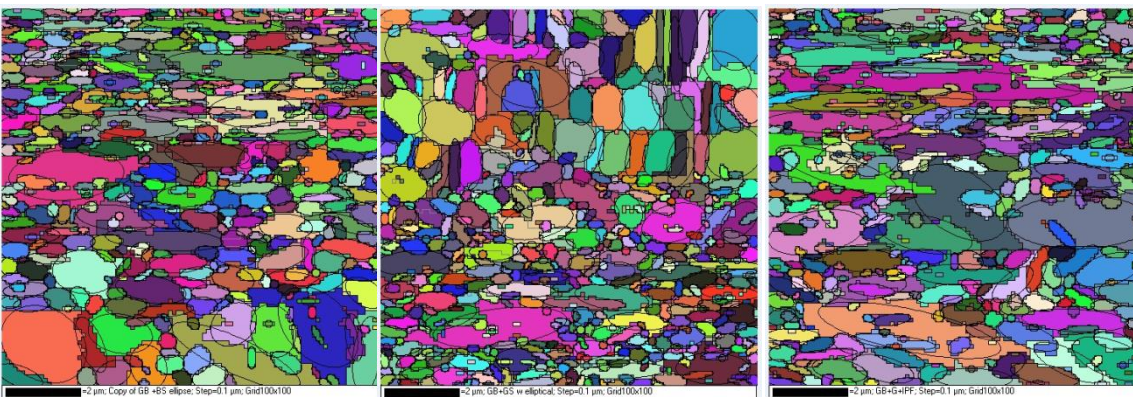

418

d) E-100

e) E-200


f) S

419

420

421

422



g) Inverse pole legend

423

424

425

426

427

428

429

430

431


432

Figure 2: EBSD images of copper deposits from EnFACE bath with different additive concentration: a) E-17 with 17% additive concentration, b) E-33 with 33% additive concentration, c) E-50 with 50% additive concentration, d) E-100 with 100% additive concentration and e) E-200 with 200% additive concentration, and f) S - standard bath. These percentages are relative to the industry recommended additive concentration of 10 ml/L Copper Gleam B, 0.5 ml/L Copper Gleam A, and 70 ppm Cl⁻. The calibration bar represents a length of 2 μm. The different colors in the EBSD map represent different crystals planes as described by the g) inverse pole legend.

433

434

435

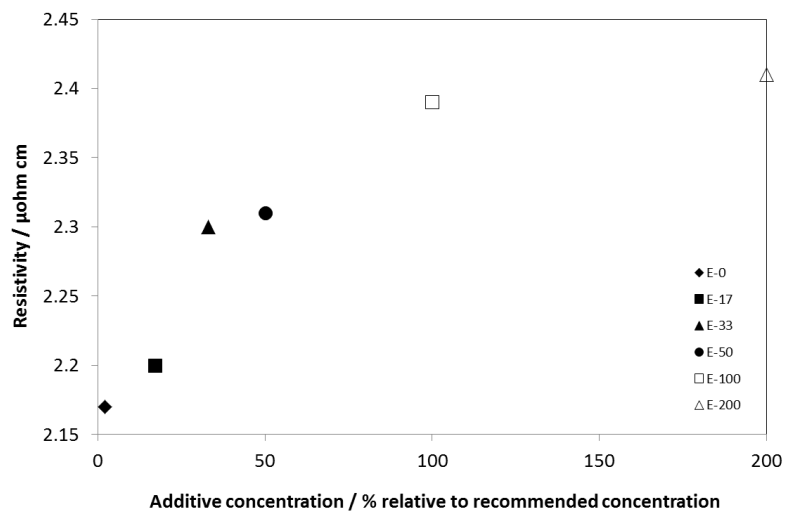

436

437 **Figure 3: Resistivity measurements of electrodeposited copper films using EnFACE**
438 **electrolyte with varying additive concentrations.**

439

440

441

442

443

444

445

446

447

448


449

450


451

452


453

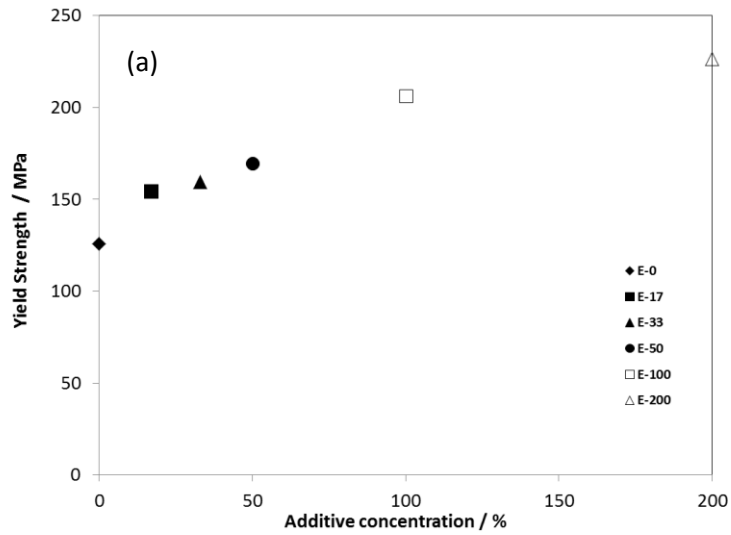

454

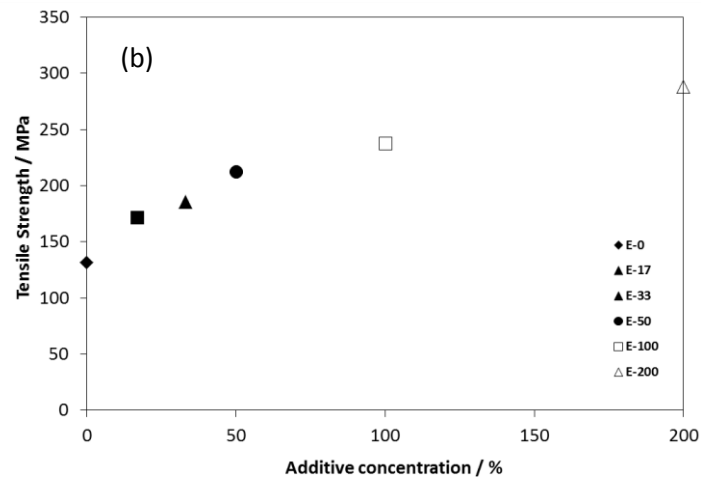

455

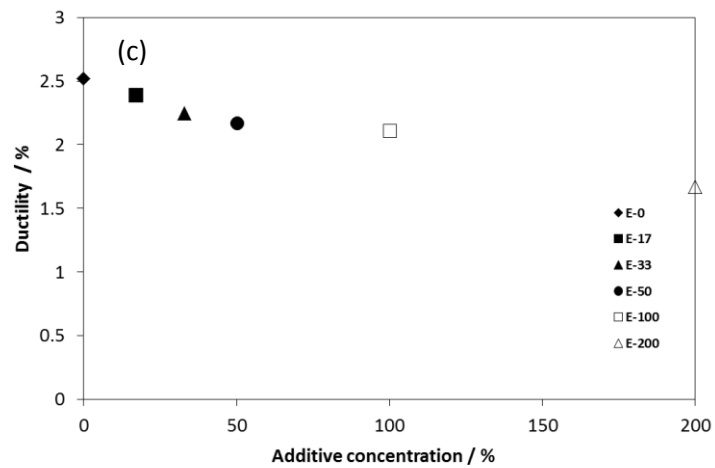

456

457 **Figure 4: The a) yield strength, b) tensile strength and ductility of plated copper films**
 458 **using EnFACE electrolyte with varying additive concentrations.**